

A COMPARATIVE STUDY OF THE PROPERTIES OF LOW CARBON ALUMINIUM-KILLED AND BORON-MICROALLOYED STEELS FOR ENAMELLING



XXI International Enamellers Congress

18 - 22 May 2008 Shanghai - China



A Comparative Study of the Properties of Low Carbon Aluminium-killed and Boron-microalloyed Steels for Enamelling

Éva Dénes¹, Judit Gergely², Ottó Szabados¹, Balázs Verő³

¹ISD DUNAFERR Zrt. Directorate of Innovation, Dunaújváros, Hungary

²Lampart Budafoki Zománc Ipari és Kereskedelmi Kft., Budapest, Hungary

³Bay Zoltán Foundation for Applied Research, Budapest, Hungary
edenes@rt.dunaferr.hu

Key words enamelling, low carbon Al-killed steel, B- microalloyed steel

Abstract The primordial goal of the R&D activity presented in this paper was the comparison of the properties of low carbon, aluminium-killed steels and boron added steels, properties which are strongly connected with the enamelling ability of these steels.

Based on the inspection results we can conclude that boron-microalloyed coils are more homogeneous concerning their mechanical properties, texture structure and hydrogen permeability (T_H value) than the Al-killed low carbon enamelling steel sheets.

Introduction

The enamelling industry of our days makes use of a wide range of base materials and the coating technologies are at least as much diversified as the substrates. Nevertheless, concerning the cold rolled steel sheets for two side enamelling we can mention three determinant steel grades:

- the low carbon aluminium-killed steel grade that we call conventional enamelling quality,
- the boron microalloyed steel and
- the IF steel apt for enamelling.

Boron-microalloyed steels can be produced by conventional metallurgy and the enamelling can be carried out by common two coatings two fire technology, besides this the boron-added steels presents better performances than low carbon Al-killed steels concerning mechanical properties, enamel adhesion and fish-scale resistance.

Experiments

More than 2000 steel samples resulting from the common industrial line and apt for two side enamelling have been investigated at ISD DUNAFERR Co. Ltd. in order to compare the properties of low carbon Al-killed and B-microalloyed steels [1]. The samples have been taken from different parts of the coils (forepart, middle, tail) and different part of the sheets (border and middle part).

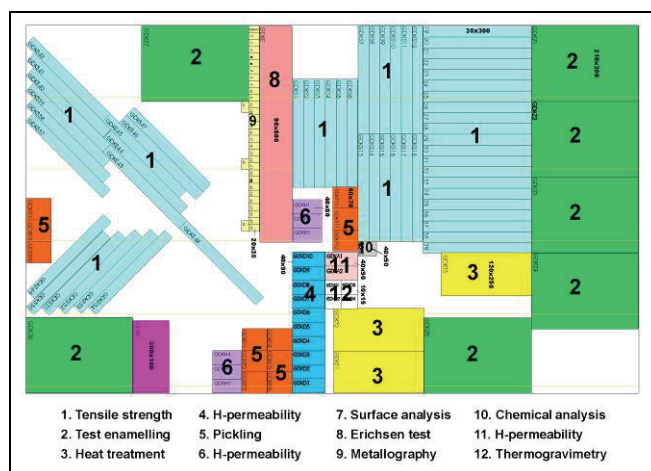


Fig. 1 Positioning of specimens for different tests

The chemical composition of the investigated samples has been the following

Table 1 The chemical composition of the investigated samples

Sample ID	w [%]						
	C	Mn	Si	S	B	Al	Ti
DC04EK (C)	0.032	0.17	0.0078	0.010	< 0.0005	0.0455	<0.005
DC04EK B (E)	0.037	0.22	0.0112	0.008	0.00302	0.0526	<0.005
DC04EK B (F)	0.04	0.21	0.0088	0.007	0.00256	0.0383	<0.001

RESULTS AND DISCUSSION

The following results have been found during the experimental work.

B-microalloyed coils samples have been more homogeneous concerning tensile strength and strain than the Al-killed ones.

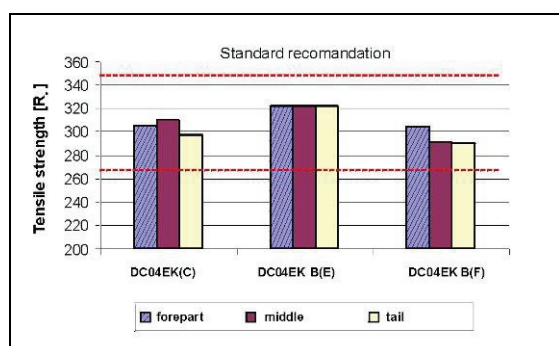


Fig. 2 Tensile strength results

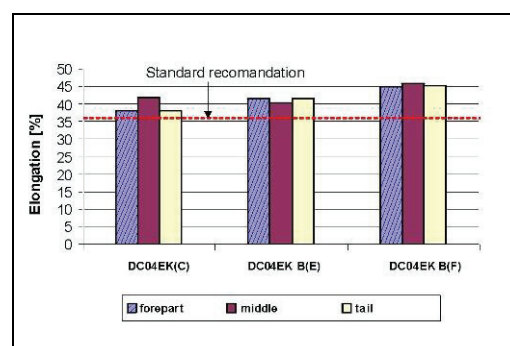


Fig. 3 Elongation of different specimens

A close relationship has been found between mechanical properties and grain size, which has been also more uniform in the case of B-added steel samples than of Al-killed ones.

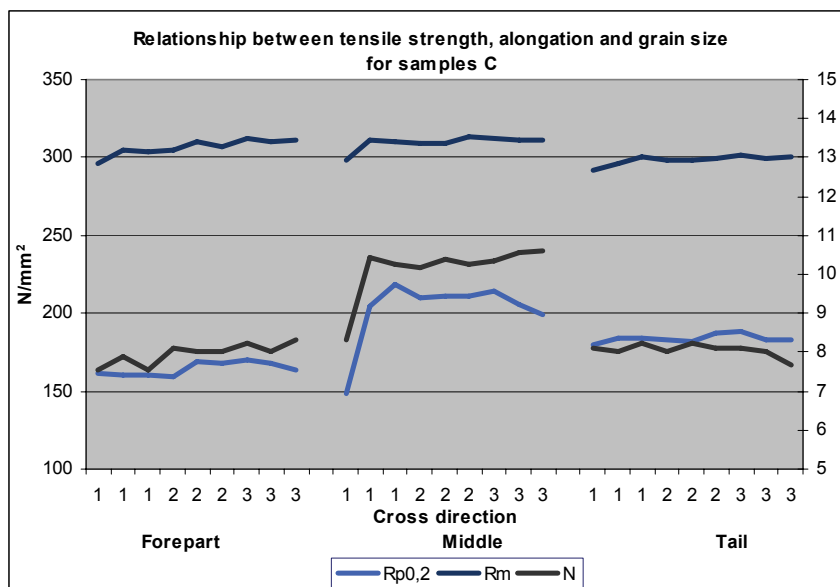


Fig. 4 Relationship between tensile strength, elongation and grain size for samples C

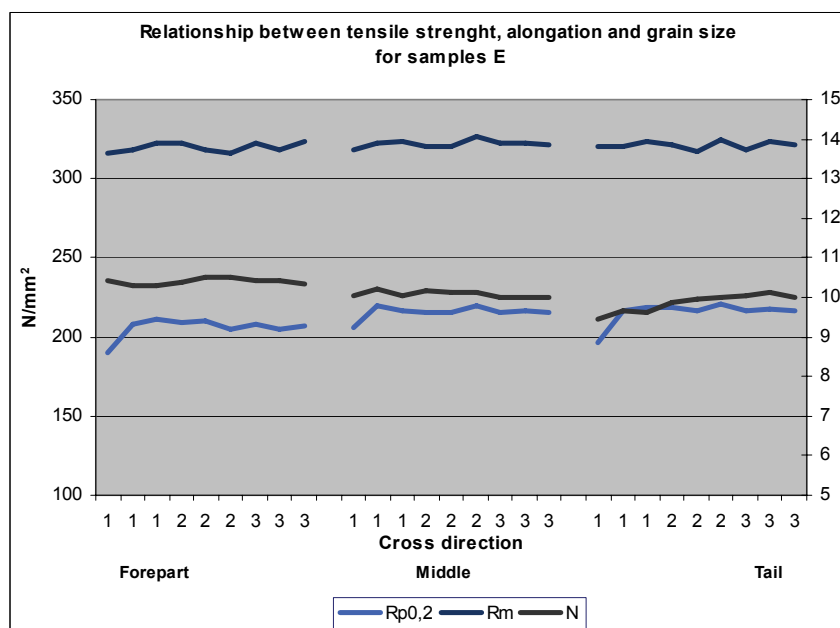


Fig. 5 Relationship between tensile strength, elongation and grain size for samples E

Table 2 Grain size values

CDE forepart			CDK middle			CDV tail		
Border	Middle	Border	Border	Middle	Border	Border	Middle	Border
7.0-8.0	8.0-9.0	7.0-8.0	8.0-11.0	7.0-9.0	8.0-11.0	7.0-9.0	8.0-9.0	7.0-8.0
EDE forepart			EDK middle			EDV tail		
Border	Middle	Border	Border	Middle	Border	Border	Middle	Border
10.0-10.5	10.5	10.0-10.5	9.5-10.5	10.0-10.5	10.0-10.5	9.0-10.0	9.5-10.5	9.5-10.0
FDE forepart			FDK middle			FDV tail		
Border	Middle	Border	Border	Middle	Border	Border	Middle	Border
9.5-10.0	9.0-10.5	9.5-10.5	8.0-10.0	8.0-9.5	8.5-10.0	7.5-9.0	7.5-8.5	8.0-9.0

The pickling loss, determined conform DIN EN 10029:2000 has been found to be higher in the case of Al-killed samples.

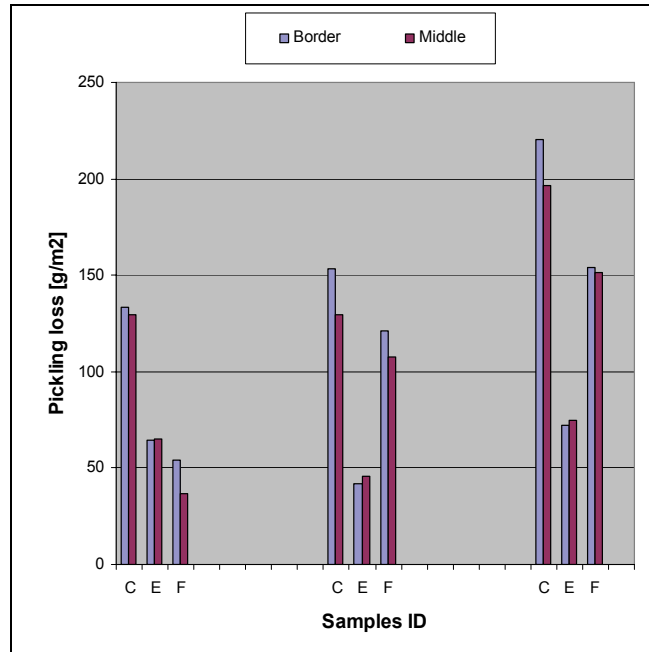


Fig. 6 Average pickling losses

The surface after pickling was smooth and uniform in the case of B-added samples, while on the pickled Al-killed test-pieces rectangular ferrite crystals can be seen alternating with smother parts.



Fig. 7 The surface after pickling of the cold rolled DC04 EK grade specimens



Fig. 8 The surface after pickling of the cold rolled DC04 EK-B grade specimens

The fish scale resistance of enamelling steels can be tested by special enamels, or hydrogen permeability measurement. In our case a special H-permeation method has been used, called Dipermet-H technique, which is more precise than the method recommended by the above mentioned standard [2,3].

The oxidation rate of Al-killed and B-microalloyed samples has been tested by thermogravimetric method [4] in different gas atmospheres and humidity after different surface pre-treatment (pickling, degreasing and Ni-coating). However the oxidation rate seemed to depend strongly from the oxidation conditions, it was general that the Al-killed samples showed always higher oxidation rate than the B-microalloyed ones.

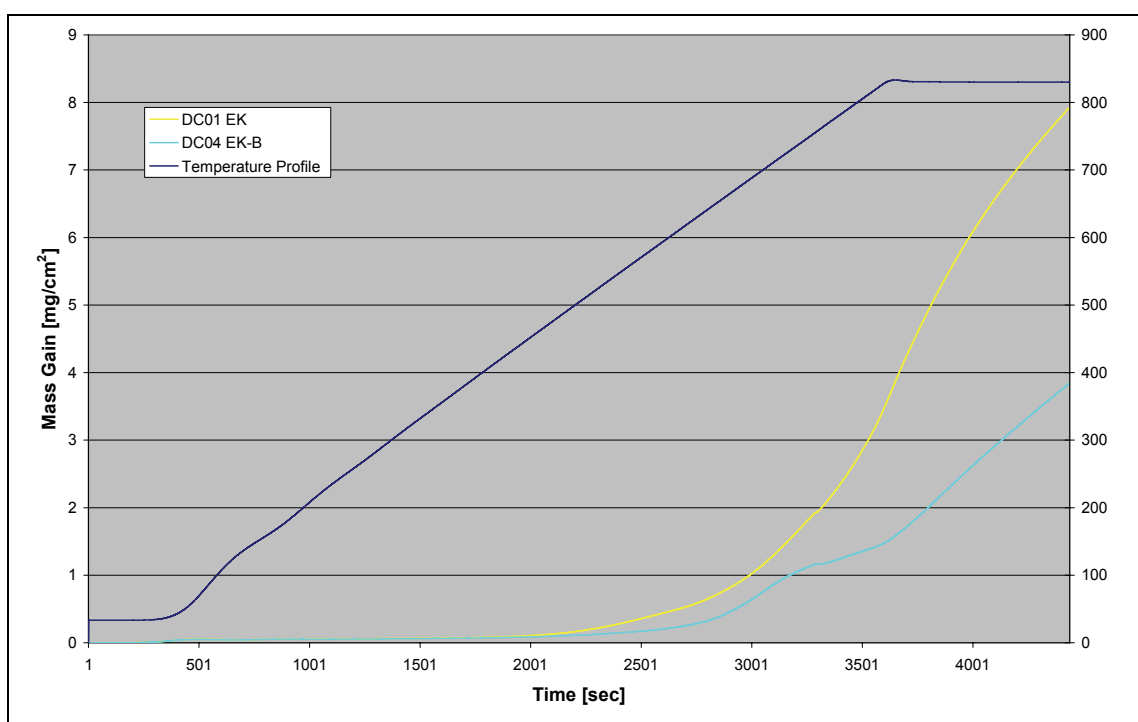


Fig. 9 The oxidation rate of DC04 EK and DC04 EK-B samples in 3% vapour containing synthetic air

Low carbon Al-killed samples showed a quite big T_H value deviation alongside the coil, which had a negative effect on the fish scale resistance reliability of the whole coil.

In the case of B-microalloyed samples the T_H values were lower, and more alike. This coils showed no fish scale defect anywhere.

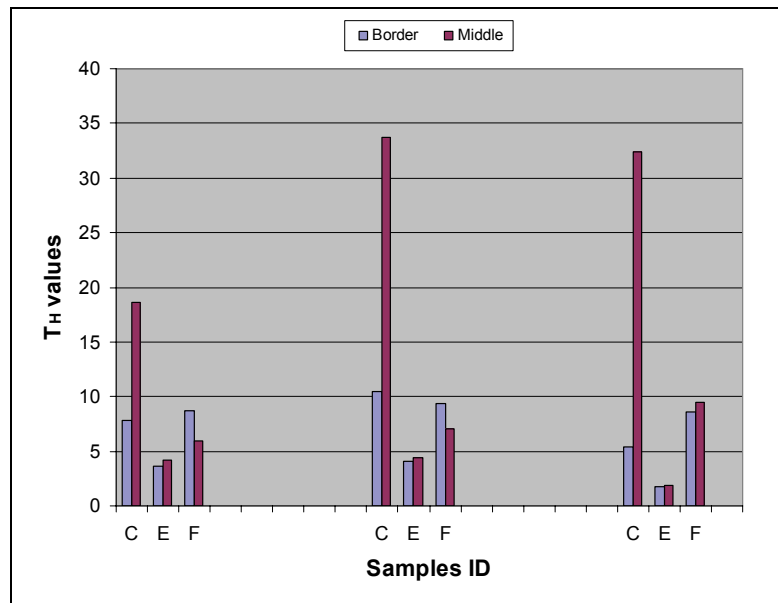


Fig. 10 T_H values of investigated samples

The fish scale phenomena can be attributed among others to the low hydrogen retention of the steel, which means a low trap's concentration.

In the case of low carbon Al killed steels trapping is done by the large massive carbides formed during the elevated roll finishing temperature [5], while in the case of boron added steels is partly attributed to the boron nitride and boron carbonitride precipitates formed during the solidification of ingots.

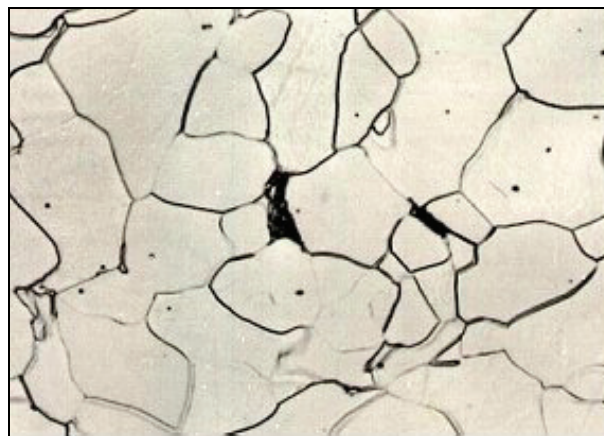


Fig. 11 The microstructure of hot rolled DC04 EK grade sample (nital, 500x)

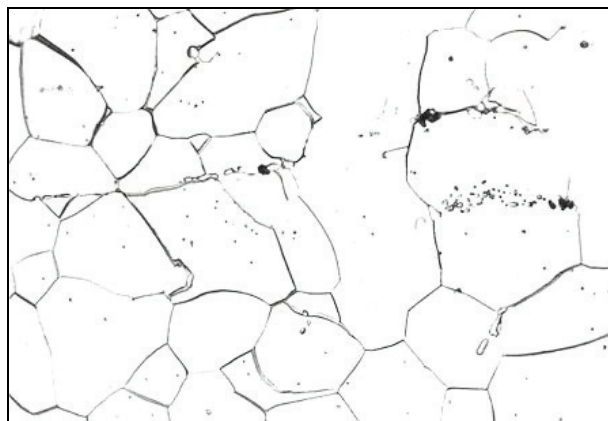


Fig. 12 The microstructure of hot rolled DC04 EK-B grade sample (nital, 500x)

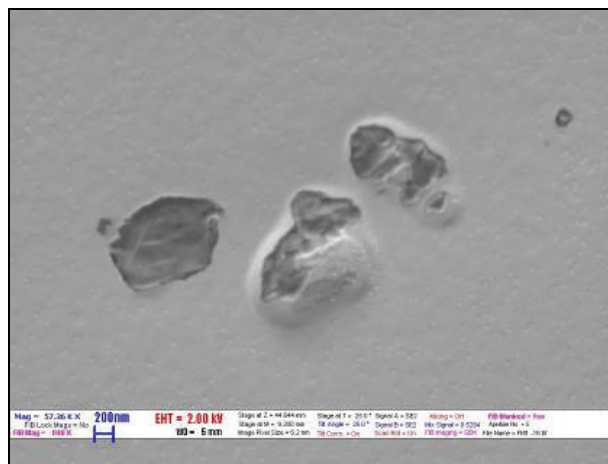


Fig. 13 SEM image of BN inclusions in hot rolled B-added sample

However cold rolling giving to at least 70% of sheet thickness reduction is sine qua non condition of the formation of hydrogen traps for both steel grades. During cold rolling the inclusions formed breaks down and shallow or deep hydrogen traps forms.

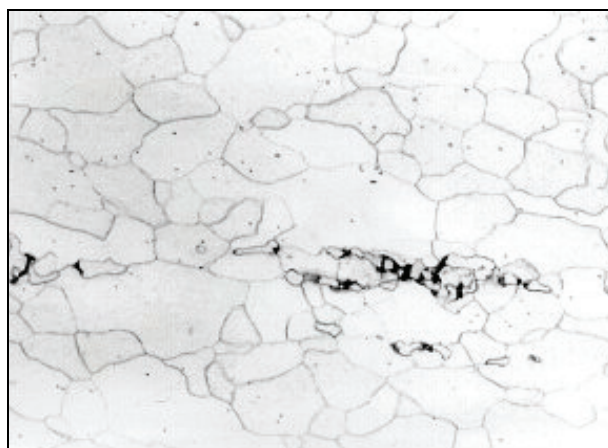


Fig. 14 Cracked carbides in cold rolled DC04 EK grade sample (nital, 500x)

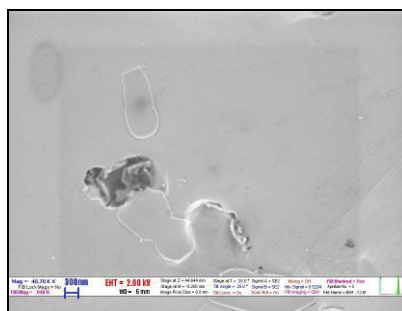


Fig. 15 SEM image of cracked BN inclusion in DC04 EK-B grade sample

Conclusion

The advantages of B- microalloyed steels are the following

- Better mechanical properties attributed to the presence of boron, which inhibits austenite recovery and recrystallisation prior to the γ/α transformation increasing the density of ferrite nucleation sites and reducing final ferrite grain size.
- Stronger enamel adhesion, which is the consequence of the more uniform pickling ability and lower oxidation rate.
- More reliable fish scale resistance due to the presence of Fe_3C , and boron containing inclusions uniformly formed during the solidification, which breaks down during the cold rolling.

Because of the very high rolling temperature ($>700^\circ\text{C}$) which should be used in order to develop large carbides in the case of Al-killed steels, the risk of temperature differences alongside the strip is higher than in the case of B-alloy steels which can be rolled at lower temperature ($<700^\circ\text{C}$). The temperature gradient can cause in-homogeneities alongside the Al-killed steel sheet coils which is detrimental to the final product's quality.

It is supposed also that boron containing precipitates do not heal during annealing as easy as the carbides in Al-killed steels and so the hydrogen trapping effect is more important and surer in the case of B-microalloyed enamelling steels. It has been proved that the T_H value of B-added steels has been increased after firing while of Al-killed ones has been decreased [6].

References

- [1] Dénes Éva, Kőszegi Szilvia: Zománcozható acéllemezek, technológiák és vizsgálati módszerek komplex fejlesztése, MZE 2002, 49. szám, 24. oldal
- [2] Dr. Péter László, Dr. Verő Balázs: Az elektrokémiai hidrogén permeációs vizsgálatok elméleti és gyakorlati vonatkozásai, MZE 2002.50. szám, 15. oldal.
- [3] L. Péter, B. Almási, B. Verő, and H. Schneider: Theoretical Analysis of Hydrogen Permeation and Entrapment Kinetics, Trans Tech Publications Ltd. Switzerland, Germany, UK, USA, 2001. p. 305.
- [4] Anna Fauszt, Balázs Verő, Éva Dénes: Thermogravimetric and Metallographic Investigation of the Oxidation of Steels for Enamelling, Trans Tech Publications Ltd. Switzerland, Germany, UK, USA, 2003. p. 195.
- [5] E. R. Fábián, B. Verő, L. Dévényi: Effect of the Microstructure of Al-killed Low Carbon Enamel-Grade Steel Sheets on Hydrogen Permeability, Trans Tech Publications Ltd. Switzerland, Germany, UK, USA, 2003. p. 201.
- [6] A. Fauszt, B. Verő, R. Takács, Á. Horváth, H. Schneider: Effect of the Enamel Firing Thermal Cycle on the Microstructure and the Hydrogen Permeability on Enamel-Grade Steels, Trans Tech Publications Ltd. Switzerland, Germany, UK, USA, 2001. p. 195.